



HexPly® M34

75°C (167°F) curing epoxy matrix

Product Data

Description


HexPly® M34 is an epoxy system, specifically developed for low temperature curing of large structural components, particularly in industrial markets.

HexPly® M34 is a self-extinguishing system, providing excellent fire-resistant properties, and meeting the German and French rail qualifications DIN 5510, S3-SR2-ST2 and NF F 16-101 (M2, F1). HexPly® M34 prepreg is ideal for manufacturing sandwich structures, providing excellent adhesion to PVC foam cores.

HexPly® M34 exhibits a good shelf life at Room Temperature for a low temperature curing system.

Benefits and Features


- Halogen free
- 10 days shelf life at RT
- Self adhesive on foam (PVC) and on honeycomb
- Low pressure moulding capability 0.8-3 bar (12-43 Psi)
- Good flexibility and handleability of prepregs
- Suitable for thick laminates - low exotherm




HexPly® M34

Resin Matrix Properties

Rheology

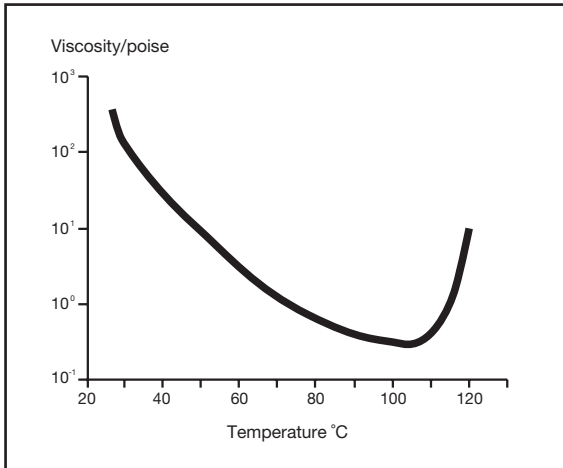

Gel Time

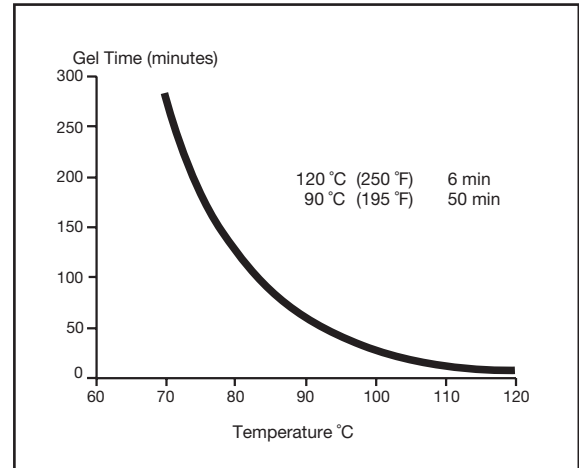

Cured Matrix Properties cured at 75°C (167°F) - 8H

Test	Values	Method
Glass transition temperature	80°C (176°F)	DMA
Cured resin density	1.26 g/cm ³	
Flexural	Str = 120 MPa (17.4 Ksi) Mod = 3.8 GPa (551 Ksi)	

Prepreg Curing Conditions

The standard cure cycle is 8 hours at 75°C (167°F), at a pressure between 0.8 and 3 bar. The following alternative cure cycles can be used:

Temperature	Time
65°C (149°F)	16 hours
90°C (194°F)	90 minutes
120°C (250°F)	40 minutes

Typical Mechanical Properties on HexPly® M34 preregs

Main references (Others available)

TEST	E-glass Balanced fabric 600 g/m ²	E-glass Balanced fabric 300 g/m ²	HS 12k carbon Balanced fabric 600 g/m ²
0° Tensile strength MPa (Ksi)	400 (58)	600 (87)	900 (130)
0° Tensile modulus GPa (Msi)	20 (2.9)	21 (3)	65 (9.4)
0° Flexure strength MPa (Ksi)	670 (97)	700 (101)	950 (137)
0° Flexure modulus GPa (Msi)	20 (2.9)	20 (2.9)	65 (9.4)
0° Compression strength MPa (Ksi)	/	540 (78)	600 (87)
0° Short beam strength MPa (Ksi)	53 (7.7)	50 (7.2)	70 (10)
Fibre volume content %	50	55	60

HS = high strength



Prepreg Storage Life

- Shelf Life @ 23 + 2 °C (73 °F) 10 days
- Guaranteed Shelf Life @ -18 °C (0 °F) 12 months

Precautions for Use

The usual precautions when handling uncured synthetic resins and fibrous materials should be observed, and a Safety Data Sheet is available for this product. The use of clean, disposable, inert gloves provides protection for the operator and avoids contamination of material and components.

Important

All information is believed to be accurate but is given without acceptance of liability. Users should make their own assessment of the suitability of any product for the purposes required. All sales are made subject to our standard terms of sale which include limitations on liability and other important terms.

©Copyright Hexcel Corporation
Publication FTA 091c (Sept 2011)

For More Information

Hexcel is a leading worldwide supplier of composite materials to aerospace and other demanding industries. Our comprehensive product range includes:

- Carbon Fibre
- RTM Materials
- Honeycomb Cores
- Carbon, glass, aramid and hybrid prepregs
- HexTOOL® composite tooling material
- Structural Film Adhesives
- Honeycomb Sandwich Panels
- Engineered Core
- Reinforcement Fabrics

For US quotes, orders and product information call toll-free 1-800-688-7734

For other worldwide sales office telephone numbers and a full address list please go to:

<http://www.hexcel.com/contact/salesoffices>